



**REGISTER now!**

**LOGIN**

Home | Authors Speak | Author Profiles | Indexing | Publication Charge | Giving Back | Contact



**Announcement :** Special Offer: SDI announces special discount of 79-96% on normal Article Processing Charge (normal APC is US\$ 500) for any manuscript submitted between **01 Dec, 2016 - 31 Dec, 2016**, as described in [Publication Charge link](#).

## Quick Menu

**Journals (A-Z)**

**Journals by Subject**

**Manuscript Submission**

**SDI in NEWS**

**Reprints**

**Subscription**

**FAQ & Help**

## Upcoming Journals

Asian Journal of  
Environment & Ecology

➔ **MORE**

## About Us

SCIENCEDOMAIN *international* (SDI) publishes high-quality, [OPEN peer reviewed](#), OPEN access international journals in various sectors of science, technology and medicine (STM). Fast and Open access principle of SDI help to promote rapid propagation of most up-to-date research findings to the researchers worldwide without any financial barrier.

**Editorial team of SDI consists of many famous scientists like:**

[Prof. Hans Verhagen](#), Head of the Risk Assessment and Scientific Assistance Department (RASA), European Food Safety Authority  
[Prof. George Perry](#), Dean, College of Sciences, University of Texas at San Antonio, USA  
[Prof. Ni-Bin Chang](#), University of Central Florida, Orlando, Florida, USA  
[Prof. Marcello Iriti](#), Milan State University, Italy  
[Prof. Rajendra D. Badgaiyan](#), University of Minnesota, Minneapolis, MN, USA  
[Prof. William Ebomoyi](#), Chicago State University, USA  
[Prof. Z. Ghassemlooy](#), Northumbria University, UK  
[Prof. Ali Nokhodchi](#), Universities of Kent and Greenwich, UK  
[Prof. Miklas Scholz](#), The University of Salford, UK  
[Dr. Fayyaz Ali Memon](#), University of Exeter, Exeter, UK  
[Prof. Luigi Campanella](#), President of Italian Chemical Society, University of Rome, Italy  
[Prof. Viroj Wiwanitkit](#), Chulalongkorn University, Bangkok, Thailand  
[Prof. En Tao Wang](#), Instituto Politécnico Nacional, México  
[Prof. Toshiaki Nikai](#), Meijo University School of Pharmacy, Nagoya, Japan  
[Prof. M. A. Orlova](#), Faculty of Chemistry, M V Lomonosov Moscow State University (MSU), Moscow, Russian Federation  
[Prof. Y. Dai](#), Associate Director of Research, Revivacor Inc. Blacksburg, VA 24060, USA

## Mission

1. Publication of **high quality, high impact, peer reviewed** research papers.
2. **Fast dissemination** of scientific findings by reducing lag time between 'submission to final publication' by introducing efficient and robust peer review management system.
3. Providing **ONLINE full text articles free of cost perpetually**, to encourage research across the world, especially in low and middle income countries.

➔ **READ MORE**

➔ **READ MORE**

## Featured Articles

**Response of Bread Wheat to Sowing Dates and the Genotypes in Morocco ...**

**On the Gravitational Shielding Phenomenon ...**

**Optimization of Process Parameters for Improved Lipase Production by Hyperthermophilic *Bacillus sonorensis* 4R ...**

**Blindness Resulting from Instillation of Miss Paris Perfume into a 2 Year Old Child's Eyes during Febrile Convulsion: Case R...**

**Treatment with CSE-1034 (Elores™) in the Management of Community Acquired Pneumonia Due to Multi Drug Resistant *Pseudomonas* ...**

**Astragalus glycyphyllos and Astragalus glycyphylloides Derived Polysaccharides Possessing in vitro Antioxidant Properties ...**

**Investigation of the Purity of Ursolic Acid Dietary Supplements ...**

**Prevalence and Risk Factors of Dental Caries among Preparatory School Children, Menoufia Governorate, Egypt ...**

**Diagnosis of Urological Cancer by 1H NMR Based Metabonomics Urinalysis: A Pilot Study ...**

**Repair and Strengthening of R.C Flat Slab Connection with Edge Columns against Punching Shear ...**

**Adsorption and Electrokinetic Properties of Catalase onto Perlite Samples ...**

**Native Vietnamese Medicinal Plants with Anti-atopic Dermatitis Activity: A Systematic Review ...**

**Effect of Selected Conditions on Spore Populations Outgrowth Dynamics and Time to Single Spore Outgrowth Distribution in *Bacillus* ...**

**Evaluation of the Relationship and Impact of Climatic Factors on West Tennessee Corn and Soybean Yields from 1955 to 2013 ...**

**An Efficient Method for Solving Linear and Nonlinear System of Partial Differential Equations ...**

**Laparoscopic Gastric Plication: Appropriate Option in Times of Crisis? ...**

**Haptoglobin Phenotype and Soluble Transferrin Receptor among Tuberculosis ...**

**Bactrim-induced Severe Thrombocytopenia in Pregnancy ...**

**A Review of the Degenerative Intervertebral Disc Disease ...**

**Foundation Soil Characterisation for a Building with Multiple Cracks at Tarkwa, Ghana ...**

➔ **MORE**

## Search this site

Search

[Advanced Search](#)

## Announcement & News

### Index Copernicus Value of British Journal of Medicine and Medical Research

We are delighted to inform that Index Copernicus (a leading indexing organization ...

### SDI journal got 35th ranking in Publons

We are delighted to announce (as of 04/01/2016) that British Journal of Medicine and Medical Re...

### Growth of SDI and world publication market

As of 2014, total 25,064 journals are competing in World market of journal publication. In 2011, tot...

### Publication and site statistics (up to Sept, 2015)

Number of submission: 22181  
(Total up to Sept, 2015) Number of published paper: 10949&n...

### PORTICO: Permanent Digital Archiving of SDI journals

SDI is happy to announce that all our journals are now permanently archived in PORTICO. Please see t...

### Index Medicus selected 15 SDI journals

We are delighted to inform that Index

➔ **MORE**

## SCIENCEDOMAIN Awards

SCIENCEDOMAIN  
international Excellence  
Award 2014

➔ **MORE**

Browser Compatibility : Mozilla firefox, Google Chrome and IE 7 & above.



[Terms & Condition](#) | [Privacy Policy](#) | [Join Us](#) | [Help](#) | [Contact Us](#)

© Copyright 2010-2016, SCIENCEDOMAIN international. All rights reserved.

## Procédure pour vérifier que cet article est indexé sur la plateforme de CASSI

Etape 1 : Aller sur le site de CASSI en tapant dans votre navigateur <http://cassi.cas.org/>

- Cet écran s'affiche



The screenshot shows the 'CASSI Search Tool Usage Agreement' page. At the top, there is the CASSI logo (a stylized blue and yellow structure) and the text 'CASSI<sup>SM</sup> A CAS SOLUTION' followed by a yellow arrow pointing to 'CAS Source Index (CASSI) Search Tool'. Below this, the title 'CASSI Search Tool Usage Agreement' is displayed. The main text explains that the tool is an online resource for researchers and librarians to find bibliographic information. It states that by accepting the agreement, users agree to use the tool for internal business purposes only. At the bottom, there are three buttons: 'I Accept', 'I Decline', and 'Usage Guidelines'. Below the buttons is the CAS logo (a stylized blue and yellow structure) and the text 'CAS<sup>®</sup> A DIVISION OF THE AMERICAN CHEMICAL SOCIETY'. At the very bottom, it says 'Copyright © 2016 American Chemical Society All Rights Reserved'.

- Accepter en cliquant sur "I accept"
- Cet écran s'affiche



The screenshot shows the main page of the 'CAS Source Index (CASSI) Search Tool'. At the top, there is the CASSI logo (a stylized blue and yellow structure) and the text 'CASSI<sup>SM</sup> A CAS SOLUTION' followed by a yellow arrow pointing to 'CAS Source Index (CASSI) Search Tool'. Below this, there is a navigation bar with links: 'Search | About | Contact Us | Help | CAS | American Chemical Society'. The title 'CAS Source Index (CASSI) Search Tool' is displayed. The main text explains that the tool is an online resource for researchers and librarians to find bibliographic information. It states that by accepting the agreement, users agree to use the tool for internal business purposes only. Below the text, there is a search form with a dropdown menu labeled 'Title or Abbreviation', a search input field, and a 'Search' button. To the right of the search input field, there is a checkbox labeled 'Exact match'. At the bottom, there is a 'SHARE' button with social media icons for Facebook, Twitter, and LinkedIn.

## 2<sup>ème</sup> étape : Rechercher l'article



[Search](#) | [About](#) | [Contact Us](#) | [Help](#) | [CAS](#) | [American Chemical Society](#)

### CAS Source Index (CASSI) Search Tool

The CAS Source Index (CASSI) Search Tool is an online resource intended to support researchers and librarians who need accurate bibliographic information. Use this complimentary tool to quickly identify or confirm journal titles and abbreviations for publications indexed by CAS since 1907, including serial and non-serial scientific and technical publications.

**Save time and effort.** Locate the bibliographic details you need quickly and easily. Search by Title, Abbreviation, CODEN, ISBN, or ISSN. Note that there is a limit of 100 answers per search, so it is recommended that you make your search as specific as possible.

**Title or Abbreviation** ▼ **Search Tips**

Select Search Option

☐ Exact match

CODEN  
ISBN  
ISSN

[SHARE](#) [f](#) [t](#) [e](#) ...

- **Sélectionner le mode de recherche dans le menu déroulant, le Titre du journal, le CODEN, le ISBN ou le ISSN.**  
Dans ce cas, Sélectionner par exemple Title ou Abbreviation
- **Taper (ou Copier et Coller) le Titre de l'article** (Ici par exemple, " *Physical Science International Journal*" ) dans le champ de recherche.
- **Cliquer sur Search**



[Search](#) | [About](#) | [Contact Us](#) | [Help](#) | [CAS](#) | [American Chemical Society](#)

### CAS Source Index (CASSI) Search Tool

The CAS Source Index (CASSI) Search Tool is an online resource intended to support researchers and librarians who need accurate bibliographic information. Use this complimentary tool to quickly identify or confirm journal titles and abbreviations for publications indexed by CAS since 1907, including serial and non-serial scientific and technical publications.

**Save time and effort.** Locate the bibliographic details you need quickly and easily. Search by Title, Abbreviation, CODEN, ISBN, or ISSN. Note that there is a limit of 100 answers per search, so it is recommended that you make your search as specific as possible.

**Title or Abbreviation** ▼ **Search Tips**

☐ Exact match

[SHARE](#) [f](#) [t](#) [e](#) ...

[Search](#) | [About](#) | [Contact Us](#) | [Help](#) | [CAS](#) | [American Chemical Society](#)

- **Cet écran s'affiche** (cet écran s'affiche si le Journal existe dans la base de données de CASSI)



[Search](#) | [About](#) | [Contact Us](#) | [Help](#) | [CAS](#) | [American Chemical Society](#)

## CAS Source Index (CASSI) Search Result

Displaying Record for Publication: [Physical Review & Research International](#)

Entry Type	Changed Title Serial
Title	Physical Review & Research International
Abbreviated Title	Phys. Rev. Res. Int.
CODEN	PRRIEM
ISSN	2231-1815
Language of Text	English
Summaries In	English
History	v1 n1 2011-v4 n2 Mar./Apr. 2014
Publication Notes	Avail. from Internet at URL: <a href="http://www.sciencedomain.org/journal-home.php?id=4">http://www.sciencedomain.org/journal-home.php?id=4</a>
Publisher Name	SCIENCEDOMAIN International
Successor Title Note	Changed to
Successor Title(s)	<a href="#">Physical Science International Journal</a>

[Disclaimer](#)

*Cet écran renseigne sur toutes les informations détaillées de l'article comme sur la photo ci-dessus.*



## Thermomechanical Characterisation of Compressed Earth Blocks Added with Sawdust

Chakirou Akanho Toukourou<sup>1,2</sup>, Guy Clarence Semassou<sup>1,2\*</sup>,  
Clément Ahouannou<sup>1,2</sup>, Sèfiou Avamasse<sup>1,2</sup>, Antoine Vianou<sup>2</sup>  
and Gérard Degan<sup>1</sup>

<sup>1</sup>Laboratoire d'Energétique et de Mécanique Appliquée (LEMA), Université d'Abomey-Calavi,  
01 BP 2009 Cotonou, Bénin.

<sup>2</sup>Laboratoire de Caractérisation Thermophysique des Matériaux et d'Appropriation Energétique  
(LABO-C.T.M.A.E.), Université d'Abomey-Calavi, 01 BP 2009 Cotonou, Bénin.

### Authors' contributions

This work was carried out in collaboration between all authors. Author CAT designed the study, wrote the protocol and wrote the first draft of the manuscript. Author GCS managed the literature searches and analyses of the study performed the spectroscopy analysis. Authors CA and SA managed the experimental process. Authors AV and GD identified the local building materials. All authors read and approved the final manuscript.

### Article Information

DOI: 10.9734/PSIJ/2016/29393

#### Editor(s):

(1) Lei Zhang, Winston-Salem State University, North Carolina, USA.

(2) Christian Brosseau, Distinguished Professor, Department of Physics, Université de Bretagne Occidentale, France.

#### Reviewers:

(1) Ishaya M. Dagwa, University of Abuja, Nigeria.

(2) Kamila Muzafarovna Gapparova, M. Auezov South Kazakhstan State University, Kazakhstan.

(3) Shodolapo Oluyemi Franklin, University of Botswana, Botswana.

(4) A. Ibe Kenneth, Federal University of Petroleum Resources, Nigeria.

Complete Peer review History: <http://www.sciencedomain.org/review-history/17087>

Original Research Article

Received 8<sup>th</sup> September 2016

Accepted 12<sup>th</sup> November 2016

Published 1<sup>st</sup> December 2016

### ABSTRACT

The study of mechanical resistances twined to standards dispositions allows keeping a composition of CEB measured out 10% of cement and 2% of *Tectona grandis* sawdust. This composite material offers a higher strength compared to the one obtained with *Azadirachta indica* sawdust. The method of asymmetric hot plan has been used to determine the thermal conductivity of the material and deduct the thermal parameter such as the diffusivity, the effusivity and calorific capacity. This method proceeds by a quadripolar modelisation 1D and allows to represent with a good precision the temperature in the center of a drill linked to the studied samples. The results that are obtained have shown that the addition of sawdust to the ordinary compressed earth blocks has clearly improved isolation performances of the final composite material.

\*Corresponding author: E-mail: [clarence.semassou@gmail.com](mailto:clarence.semassou@gmail.com);

**Keywords:** Compressed earth block; sawdust; mechanical resistance; thermal parameters.

## NOMENCLATURES

$a$	: Thermal diffusivity ( $m^2.S^{-1}$ )
$BTC$	: Compressed earth block (CEB)
$CEB 10$	: CEB dosed at 10% cement
$CEB 8$	: CEB dosed at 8% cement
$CEB 6$	: CEB dosed at 6%
$C_p$	: Calorific capacity $J.m^{-3}.K^{-1}$
$E$	: Separation between (cm)
$F$	: Maximal charge supported by two half block (kN)
$V$	: Volume ( $m^3$ )
$F'$	: Resistance to tests compression, $MN/m^2$
$GTR$	: Earthworks Road Guide
$H$	: Thickness of the blocks (cm)
$L$	: Width of the blocks (cm)
$M$	: Mass of the material (kg)
$P$	: Charge at the break (KN)
$S$	: Average surface of tests face ( $cm^2$ )
$X$	: Water content ( $kg\ water.kgms^{-1}$ )

## Greek Symbols

$\lambda$	: Thermal conductivity ( $W.m^{-1}.K^{-1}$ )
$\rho$	: Volumic mass ( $kg.m^{-3}$ )

## Subscripts

$a$	: Apparent
$b$	: Test
$e$	: Water
$ec$	: Sample
$h$	: Wet
$i$	: Initial
$X_{op}$	: Optimal water contents
$S$	: Dry

## 1. INTRODUCTION

The recent researches on the local material have shown that the earth offers a great potentiality to the different need of human beings. Houben H. and Guillaud H. have precised that, this kind of material doesn't really get, at natural state that people wanted to grant it, the thermal performances [1]. Nevertheless, when the earth material was mixed to other materials, these external, like fibrous materials and the linking, participate to the improvement of its performances, as well mechanic as thermal one. So the sawdusts generally are raised to be suitable as adjuvant in earth composite materials [2-5]. In practice, wood processing companies in

developing countries generate more than 30 to 50% of the waste treated wood volume, according to the case. These wastes are often used as a solid fuel, which promotes consequently the substantial production of carbon dioxide ( $CO_2$ ): a greenhouse gas, which contributes to the destruction of the ozone layer [6].

In order to participate to the fight against the degradation of environment many researchers are interested on nowadays in the valorization of wastes, the recycling. It's in this context that this study has permitted to explore the possibilities of compressed earth blocks utilization with sawdust addition.

## 2. MATERIALS AND METHODS

### 2.1 Materials

Sample material which constitutes the basic element for our study is a laterite composite + cement + sawdust + water in good studied propositions.

#### 2.1.1 The earth

The laterite used is from Woba Karou in N'dali district See Fig. 1 (area located in the Northern Benin in the department of Borgou). The Fig. 1 show the geographical location of the sampling site of laterite.

#### 2.1.2 The cement


The cement portland CPJ 35 has been used for this study because of its relative quick adherence.

#### 2.1.3 The sawdusts

The sawdusts of two species of tropical woods have been exploited. Afzelia and teck woods are concerned, recognized for their availability in Benin.

#### 2.1.4 The stove and the scales

A ventilated stove of Memmert mark DO6060, functioning between the temperatures range (T) as  $30^\circ C \leq T \leq 225^\circ C$  with a ventilation register, setting from 0 to 6, has permitted to dry the sawdust sample and to determine the dry extracts of compressed earth blocks (CEB). Two scales Sartorius type (precision 0.01 g) and

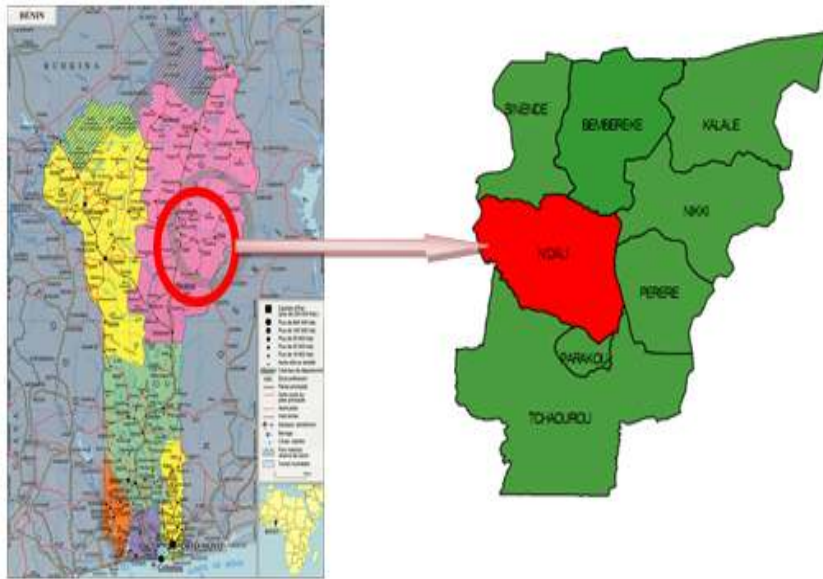

**Fig. 1. Geographical location of the sampling site of laterite**

Roverbal with a respective weight expanse of 3100 g and 20 000 g, have been used for the different internal weights forming the mixture. A belcher of 500 ml capacity has allowed to determine the volume of water constituting the block sample composition. The water that is used is the one supplied by National Society in charge of water in Benin.


#### **2.1.5 Hydraulic press (squeezer)**

It's a mechanic squeezer type SATEC MKIII-60 TVI, equipped with a command console digital hill porting. It has been used for resistance tests in flexion of three points and in compression.

## **2.2 Methods**

### **2.2.1 Physical characterization of the laterite**

In this part of the study, we have been interested on the characterization of the laterite of Woba Karou careers. This characterization consisted on the determination of physical properties like: the water content, the granulometry, the Atterberg limits, the volumic mass in bulk, the compressibility, the equivalent in sand and the real volumic mass of the produce ante-dried (Specific weight) [7,8]. Fig. 2 illustrates the particle size of the earth.

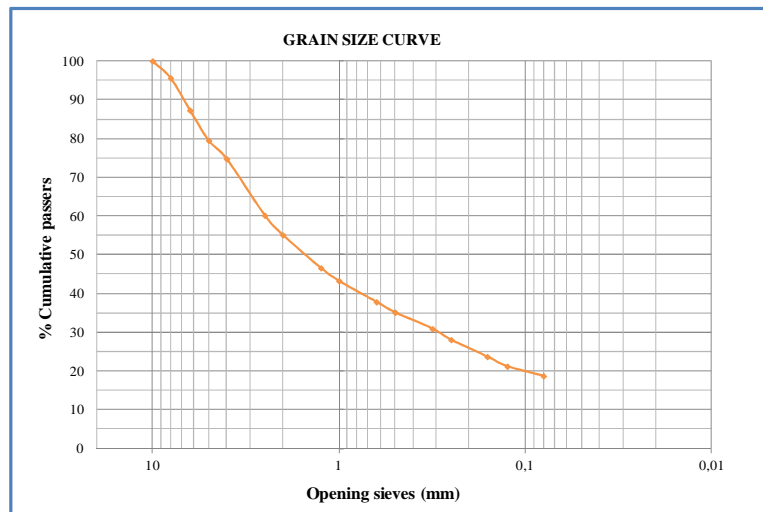

**Fig. 2. Grading curve of the laterite**

### 2.2.2 The cement

The cement portland CPJ35 used has been preserved in better conditions of temperature and humidity during 7 days in order to reach its maximal resistance to permit the relative quick use.

### 2.2.3 The sawdust

Sawdust samples treatment consisted on soaking in hot water previously brought at 105°C during 48 h. The mixture obtained has been decanted and cooled down. The soaking water cooled down has been removed and replaced by the current water. The saw dusts have been neatly cleaned. The washing water has been filtered and replaced by current water in which the sawdust has been rinsed out. This approach permits on the one hand to dissolve in water inhibition extractible substances contained in the sawdust, and on the other hand to eliminate the microorganisms eventually present inside the sawdusts. The sawdusts neatly cleaned have been recuperated and piet inside the stove (oven) at 105°C during 72 h.

Out of the oven, they has been spread on a tray and preserved in atmosphere conditions for 24 h to be adapted to atmosphere conditions. The sawdusts of each wood genus are examined closely and the fractions of sawdusts of granular class 0.16-5 mm have been packed and preserved far from humidity and heat under closed package until CEB realization.

### 2.2.4 Test realization (BTC)

- ✓ Cycle of compressed earth production

A pre-treatment by sieving, with sieve of stitch of 10 mm laterite destined to the confection of EBC has been useful because of the presence of big particles in the earth samples, which have been spread in thin lagers at atmosphere temperature during 7 days in order to insure a natural drying. The water content of laterite has been determined  $X_{cc}$  in order to deduce the indispensable water volume to the composite mixture. In the same way, the masses of different components contributing to the preparation of dry mixture have been obtained. An adequate mixture of laterite + cement + sawdust + water has been realized and introduced into the press for the confection of CEB.

- ✓ Water volume of production

Messing water has been progressively brought until the mortar is brought to the optimal content in water ( $X_{op}$ ) of the earth determined for Proctor test. So the volume of water in liter to add has been given by the following formula:

$$V_e = \frac{(X_{op} - X_{ec})M_1}{100 + X_{ec}} \quad (1) [3]$$

Tests production CEB has been done according following the important steps: extraction, preparation, mixture, pressing, treatment and storing.

- ✓ Massic composition of CEB tests

Table 1 informs on massic composition of different mixtures (laterite + cement + sawdust + water) realized for the sampling.

**Table 1. Massic composition of CEB tests**

	Laterite (Kg)	Sawdust (Kg)	Cement (Kg)	water (L)
CEB dosed at 4% of sawdust	7,74	0,36	0,9	0,5
CEB dosed at 6% of sawdust	7,56	0,54	0,9	0,5
CEB dosed at 8% of sawdust	7,38	0,72	0,9	0,5
CEB6	8,46	*	0,54	0,5
CEB8	8,28	*	0,72	0,5
CEB10	8,1	*	0,9	0,5
CEB dosed at 2% of sawdust	7,92	0,18	0,9	0,5

- ✓ Treatment and storage of blocks

The local where the blocks are manufactured is well isolated from solar radiance and the treatment has been done under a transparent covering of polyster. This precaution has permitted after the 7<sup>th</sup> day of preservation to prolong the treatment opened in the local without damages on the blocks.

### 2.2.5 Mechanical characterization of CEB

In the context of this study, we have been interested in classical characteristics as below: the resistance in inflexion three points, in compression. For the test of resistance in flexion

in three points, the block support face has been installed on two tubes spaced out of 20 cm and perpendicular to the block length, in the middle of the superior face, a third tube parallel to the firsts has been installed. We submit the CEB test to a constant charge at the rupture. The resistance to the blocks flexion has been determined by the formula:


$$\sigma = \frac{1.5 * E * P}{L * H^2} \quad (2)$$



**Fig. 3. Test of resistance in inflexion (three points) on CEB**

That is adopted the procedure for resistance in compression test has also permitted to take the two halves of the test CEB stemming from flexion in three points tests. The two half – blocks were not always identical with regular forms. So the section held for the calculations is the mean average of the surfaces inferior and superior of the half-blocks. The resistance to the compression has been obtained by the formula:

$$F'_{sec} = 10 * \frac{F}{S} \quad (3)[9]$$

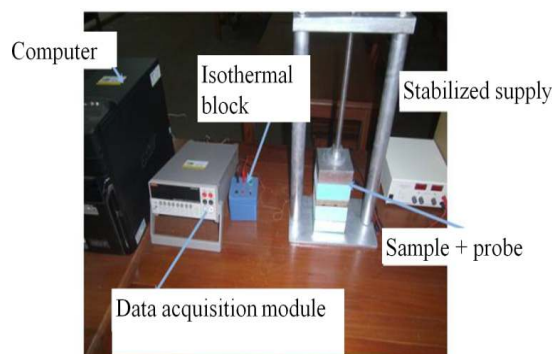

**Fig. 4. Experimental mechanism of thermal characterization of experience test**

## 2.2.6 Thermal characterization of CEB

The thermal properties assessed in the context of this work are: thermal conductivity, thermal diffusivity, the effusivity, calorific capacity. The method chosen here is the « asymmetric hot plan » method materialized by the picture below. We have used a program of simulation on support « Matlab » for the estimation of thermal parameters.

## 3. RESULTS AND DISCUSSION

### 3.1 Mechanical Characteristics of CEB


The laterite water content sampled at Woba karou is estimated at 1.3%. Its granularity was inferior to 35% and the percentage of fines is about 17.23%.

The maximal diameter of grains is about 10mm (inferior to 50mm). Referring to the standards of classification NFP 11-300 and the GTR 92, we can deduce that the laterite used for our study belongs to class B (it has thus been sampled in sandy ground and grave lows one with fines) [10]. This assertion is confirmed by the theory about Atterberg limits in which the plasticity indice found is about 15.66% (superior to 12%), what allows to conclude with precision that laterite sample belongs to the under class B6. (Sand and clay grave to very clayer). Moreover, this type of laterite replies to Ramillon and Cratere granulometric standard, which recommends that fines percentage must be between 15 and 30% so as to be used for CEB manufacturing. According to the standards ARS 681: 1996 compressed earth blocks good manufacturing process in manufacturing of earth mortar, the earth of under –class B6 were acceptable for realization of CEB, Consequently, Woba Karou laterite can be used for CEB realization [4,11,12].

Proctor tests permit to emphasize on the following characteristics for the studied laterite: an optimal water contents ( $X_{op}$ ) about 5,82% and a maximal dry density ( $\gamma_{dmax}$ ) about 2,27 T.m<sup>-3</sup>.


Beyond these characteristics, we can notice that the consistence indice  $I_c > 1.3$  So according to the standards NFP 11-300 and knocking down transport (KDT), the laterite used was at a very dry state; its equivalent in sand is  $E_s=20\%$ , this confers to this material a perfect stability and a sawdust textures [10]. Its use for the CEB is thus possible and can provide good results. The

cement CPJ 35 from SCB Lafarge society has been used for the composition of the sampled mixture. It was produced according to the standard, NF P15-301 and allows a relatively rapid taking [13]. The third constituent of the mixture is the sawdust stemming from wood species: *Azalia africana* and *Tectona grandis*.

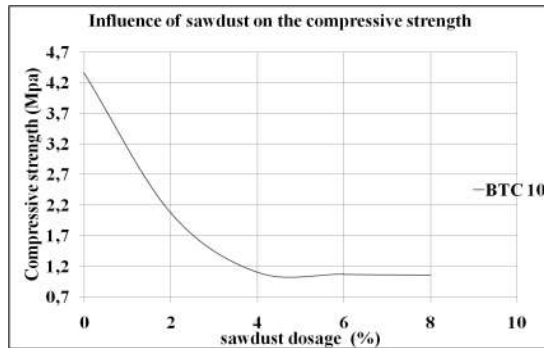

**Fig. 5. Influence of dosage of Afzelia sawdust on the resistance in compression**


The Figs. 5 and 6 present the influence of measuring out of Afzelia sawdust in the resistance in compression and inflexion in three points. Between 0 and 3% average, we notice a rapid decreasing of CEB resistance in which stabilizes at an average value about 1 Mpa for the resistance in compression and about 0.23 for the resistance in three points flexion.

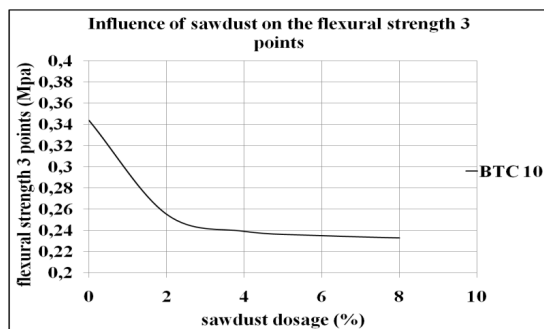


**Fig. 6. Influence of dosage of Afzelia sawdust on the resistance in three points flexion**

The mechanical performances of CEB with addition of sawdust are reversely proportional to the sawdust quantity inside the composite mixture the works of Solomon-Ayeh supported by the standards ARS 674:1996 and ARS 675:1996 indicate that a CEB material can be used in building when its resistance in compression is superior to 2MPa [6,9,14]. We will also retain that the content in cement has an influence on

the mechanical resistances of CEB studied this influence has an increasing look and linear for the case of resistance in flexion, with a minimum in the coordinates points (6; 0, 27). As for the resistance in compression, it is proportional to the content in water, with a minimal value around 2.25 Mpa.

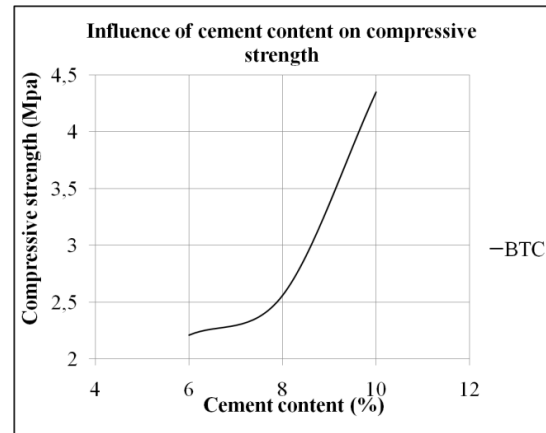

**Fig. 7. Influence of cement content on the resistances in compression**

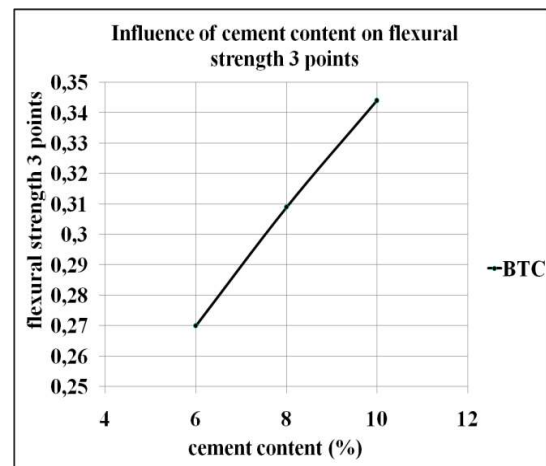

**Fig. 8. Influence of cement content on the resistances in flexion three points**

The curves of Figs. 7 and 8 show up to an addition of 10% of cement, the mechanical resistances of CEB rise in proportion with cement dosage. Consequently, the mixture sample of CEB studied has been dosed at 10% in cement. Peltier correlation (8) presented in the formula (3) expresses the optimal water content offering a maximal resistance for the test in flexion in three points. This expression has been retaken by Olodo and Rigassi who confirmed it has been

applicable for the case that the CEB is without addition. For this study, the samples-test in CEB has been realized by compressed earth block (CEB) with addition of sawdust [15,16]. Assembling the sawdust to a granular material and making analogy between the two types of CEB with and without sawdust addition, we theoretically deduce that the optimal water content of CEB with Afzelia sawdust has permitted to reach a water volume of wasting in level of  $V_e = 470$  cl. The experimental curve of Fig. 9 presents a value  $V_e = 460$  Cl, which corresponds to a maximal resistance in flexion three points. So, a relatively very weak interval of (2.12%) in touch with obtained values  $V_e$  has been noted; that permits to conclude that the correlation is well applicable for the studied CEB with sawdust addition

### 3.2 Mechanical Characteristics of CEB with Sawdust Addition

The graphs of Figs. 10 and 11 give a general idea of mechanical resistances of CEB with addition of sawdust coming from essences of *Tectona grandis* and *Afzelia africana*.

The composites on the basis of *Tectona grandis* sawdust shows a resistance sensitively superior to those elaborated on the basis of *Afzelia africana* sawdust. The values of the resistance obtained for the two realized tests respect the requirements of Standards ARS674: 1996 and ARS 675: 1996.

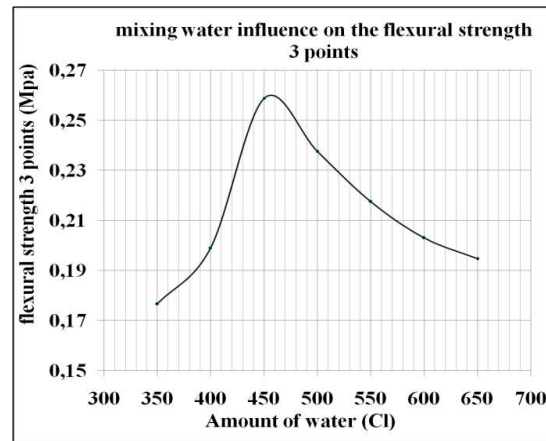


Fig. 9. Influence of wasting water on the resistance in flexion three points

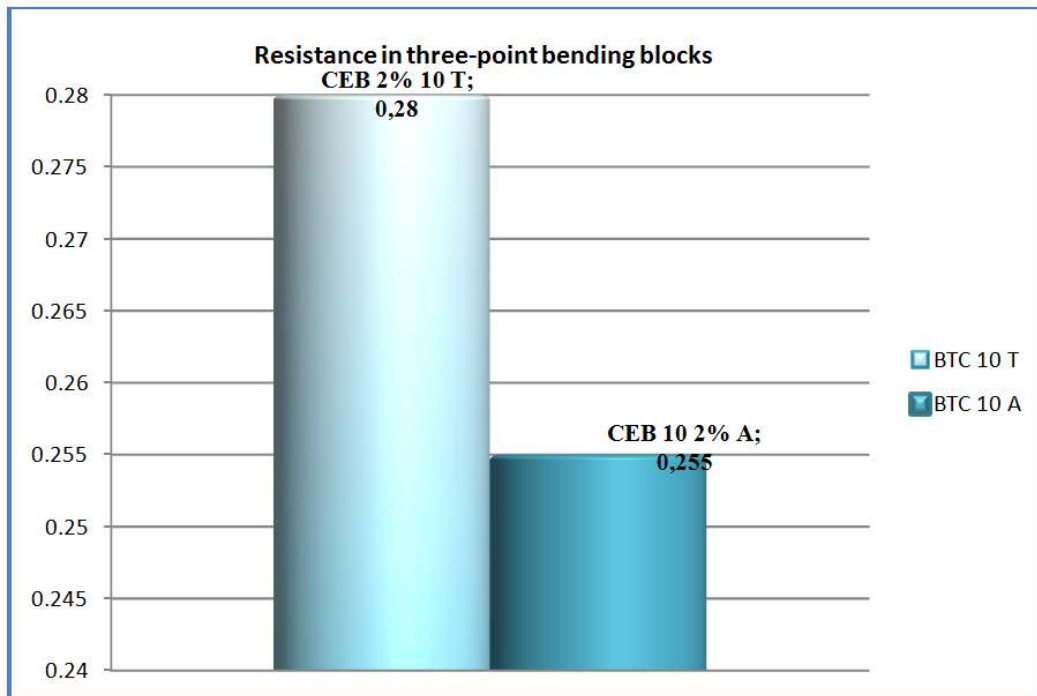
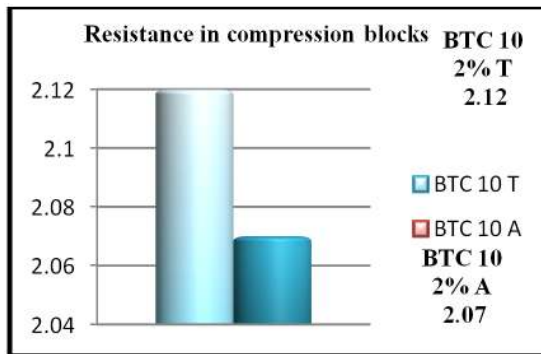


Fig. 10. Resistance in flexion three points and in compression with *Afzelia africana* and *Tectona grandis* sawdusts


**Table 2. Thermal characteristics values evaluated for CEB 10 and CEB 10- T-2%**

Parameters	Average values						
	Thermal effusivity	Uncertainty on thermal effusivity%	Thermal conductivity $\lambda \text{ w.m}^{-1}.\text{K}^{-1}$	Uncertainty on thermal conductivity %	Thermal diffusivity $\text{m}^2.\text{S}^{-1}.\text{10}^{-7}$	Calorific capacity $\text{J. m}^{-3}.\text{K}^{-1}$	Estimated times
CEBC 10	1811.00	0.45	1.70	1.10	8.91	1925759.79	350
Standard deviation	54.37		0.08		0.26	2932.49	
CEB 10-T-2%	1317.89	0.02	0.85	0.08	4.16	2042773.42	650
Standard deviation	1.83		0.01		0.09	22968.73	

**Fig. 11. Resistance in flexion three points and in compression with *Azelia africana* and *Tectona grandis* sawdusts**

### 3.3 Thermal Characteristics of CEB with or without Sawdust Addition

The results obtained for the CEB 10 at the end of thermal test are presented in the Fig. 10.

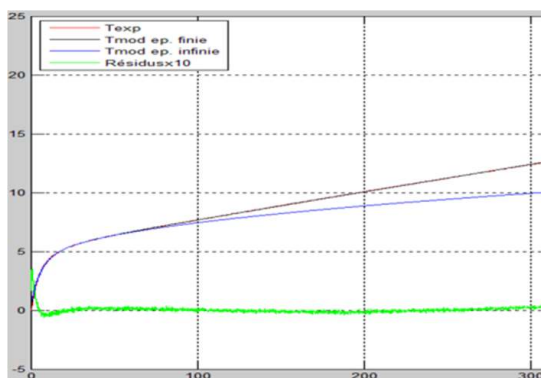**Fig. 12. Curve experimental model and testing of residues on the sample 10 BTC**

The theoretical and experimental curves are superimposed perfectly and the residues are well equally flat. This confirms the accuracy of operations.

## 4. CONCLUSION

These reports enumerated above show CEB incorporating *Tectona grandis* sawdust constitute an isolant which could play a very interesting role in the field of energetic efficiency. The values of thermal parameters wanted for BTC 10-7-2% and BTC-10 as following: calorific capacity, thermal diffusivity thermal effusivity and thermal conductivity are summarized in the Table 2. The blocks without sawdust addition present effusivity and thermal conductivity values superior to those of CEB with addition. This means that the conduction of heat by a material is intimately linked to thermal conductivity and to the effusivity. It stands out from this that CEB incorporating *Tectona grandis* sawdust conducts less heat. It's the same thing for the CEB with sawdust addition which diffuses less heat than classic CEB. Besides, as the table 2 presents it at 2% of sawdust addition; CEB gets a better calorific capacity. Consequently our material, in addition to the fact that in limits heat conduction, it gets a strong capacity of storing.

## COMPETING INTERESTS

Authors have declared that no competing interests exist.

## REFERENCES

- Houben H, Guillaud H. Traité de construction en terre. 2 ed. [earth construction processed] Parenthèses, Marseille; 1995.
- Franz V. Constructeur en terre allégée, [Earth construction lightened] Actes Sud 2016 pour l'édition Française; 2016. Available:[www.Actes-sud.fr](http://www.Actes-sud.fr)
- Jannot Y, Felix V, Degiovanni A, Bal H. A centered hot plate method for measurement of thermal properties of thin

- insulating materials. Measurement Science and Technology. 2010;21(3).
4. Toukourou CA, et al. Mechanical characterization of an eco-material: Case of compress earth bloc (CEB) with addition of cotton waste. Int. J. Cur. Tr. 2015;4(1):109. ISSN: 2278-8042.  
Available:[www.injctr.com](http://www.injctr.com)
5. Laetitia F, Romain A. Bâtir en terre du grain de sable à l'architecture [Build earthen grain of sand to architecture] éditions-Belin; 2013.  
Available:[www.editions-belin.com](http://www.editions-belin.com)
6. Ulrich R, Christof Z. Construire en terre crue, [Build earthen] Edition Le Moniteur; 2013.
7. Peltier M. Contribution à l'étude de la géotechnique routière en France et dans nos territoires d'Outre-mer, [Contribution to the study of road geotechnics in France and in our overseas territories] Paris. 1950;450.
8. Organisation Régionale Africaine de Normalisation. Ed. blocs de terre comprimée: normes. Technologie n°11. CDI et CRATerre-EAG, ARS 674: 1996, Belgique, Mars. 1998;51-55. [African Regional Organization for Standardization, Ed. Compressed Earth Blocks: Standards. Technology No. 11. CDI and CRATerre-EAG, ARS 674. 1996- compressed earth blocks Technical Specification for ordinary compressed earth blocks, Belgium]. 1998;51-55.
9. Organisation Régionale Africaine de Normalisation. Ed. blocs de terre comprimée: normes. Technologie n°11. CDI et CRATerre-EAG, ARS 674 :1996, pp47-50, Belgique, mars; 1998. [African Regional Organization for Standardization, Ed. Compressed Earth Blocks: Standards. Technology No.11. CDI and CRATerre-EAG, ARS 674. 1996- compressed earth blocks Technical Specification for ordinary compressed earth blocks, Belgium]. 1998;47-50.
10. NFP 11 300:1992 Earthworks - Classification of materials for use in the construction of embankments and capping layers of road infrastructures.
11. Organisation Régionale Africaine de Normalisation, Ed. Blocs de Terre Comprimée: Normes. Technologie n° 11. CDI et CRATerre-EAG, ARS 681:1996- Blocs de terre comprimée Code de bonne pratique pour préparation des mortiers de terre. Belgique, Mars. 1998;87-98. [African Regional Organization for Standardization, Ed. Compressed Earth Blocks: Standards. Technology No. 11. CDI and CRATerre-EAG, ARS 681: 1996- compressed earth blocks Code of Practice for Preparation of Earth Mortars, Belgium]. 1998;87-98.
12. Organisation Régionale Africaine de Normalisation, Ed. Blocs de Terre Comprimée: Normes. Technologie n° 11. CDI et CRATerre-EAG, ARS 675 :1996- Blocs de terre comprimée Spécification techniques pour les blocs de terre comprimée ordinaire. Belgique, Mars. 1998;47-50. [African Regional Organization for Standardization, Ed. Compressed Earth Blocks: Standards. Technology No. 11. CDI and CRATerre-EAG, ARS 675: 1996- Compressed Earth Blocks Technical Specification for Ordinary Compressed Earth Blocks, Belgium]. 1998;47-50.
13. NFP 15 301:1994 Hydraulic Binders - Common Cements - Composition specifications and conformity criteria.
14. Solomon-ayeh KA. Studies of strengths of stabilized laterite blocks and rendering mortars. Building Research and Information. 1994;22(3).
15. Olodo D. Murs en terre stabilisée et structures en béton de terre, [stabilized earth walls and ground concrete structures] CBRST, CNERTP. 1999;30.
16. Rigassi V. Blocs de terre comprimés, vol Manuel de production, CraTerre. [Compressed earth blocks, vol production Manuel CraTerre] 1994;63.

© 2016 Toukourou et al.; This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Peer-review history:  
The peer review history for this paper can be accessed here:  
<http://sciencedomain.org/review-history/17087>